

11.23 Taconite Ore Processing

11.23.1 General¹

The taconite ore processing industry produces usable concentrations of iron-bearing material by removing nonferrous rock (gangue) from low-grade ore. The six-digit Source Classification Code (SCC) for taconite ore processing is 3-03-023. Table 11.23-1 lists the SCCs for taconite ore processing.

Taconite is a hard, banded, low-grade ore, and is the predominant iron ore remaining in the United States. Ninety-nine percent of the crude iron ore produced in the United States is taconite. If magnetite is the principal iron mineral, the rock is called magnetic taconite; if hematite is the principal iron mineral, the rock is called hematic taconite.

About 98 percent of the demand for taconite comes from the iron and steel industry. The remaining 2 percent comes mostly from the cement industry but also from manufacturers of heavy-medium materials, pigments, ballast, agricultural products, and specialty chemicals. Ninety-seven percent of the processed ore shipped to the iron and steel industry is in the form of pellets. Other forms of processed ore include sinter and briquettes. The average iron content of pellets is 63 percent.

11.23.2 Process Description^{2-5,41}

Processing of taconite consists of crushing and grinding the ore to liberate iron-bearing particles, concentrating the ore by separating the particles from the waste material (gangue), and pelletizing the iron ore concentrate. A simplified flow diagram of these processing steps is shown in Figure 11.23-1.

Liberation is the first step in processing crude taconite ore and consists mostly of crushing and grinding. The ore must be ground to a particle size sufficiently close to the grain size of the iron-bearing mineral to allow for a high degree of mineral liberation. Most of the taconite used today requires very fine grinding. Prior to grinding, the ore is dry-crushed in up to six stages, depending on the hardness of the ore. One or two stages of crushing may be performed at the mine prior to shipping the raw material to the processing facility. Gyratory crushers are generally used for primary crushing, and cone crushers are used for secondary and tertiary fine crushing. Intermediate vibrating screens remove undersize material from the feed to the next crusher and allow for closed-circuit operation of the fine crushers. After crushing, the size of the material is further reduced by wet grinding in rod mills or ball mills. The rod and ball mills are also in closed circuit with classification systems such as cyclones. An alternative to crushing is to feed some coarse ores directly to wet or dry semiautogenous or autogenous grinding mills (using larger pieces of the ore to grind/mill the smaller pieces), then to pebble or ball mills. Ideally, the liberated particles of iron minerals and barren gangue should be removed from the grinding circuits as soon as they are formed, with larger particles returned for further grinding.

Concentration is the second step in taconite ore processing. As the iron ore minerals are liberated by the crushing steps, the iron-bearing particles must be concentrated. Because only about 33 percent of the crude taconite becomes a shippable product for iron making, a large amount of gangue is generated. Magnetic separation and flotation are the most commonly used methods for concentrating taconite ore.

TABLE 11.23-1. KEY FOR SOURCE CLASSIFICATION CODES FOR TACONITE ORE PROCESSING

Key	Source	SCC
A	Ore storage	3-03-023-05
B	Ore transfer	3-03-023-04
C	Primary crusher	3-03-023-01
D	Primary crusher return conveyor transfer	3-03-023-25
E	Secondary crushing line	3-03-023-27
F	Secondary crusher return conveyor transfer	3-03-023-28
G	Tertiary crushing	3-03-023-02
H	Tertiary crushing line	3-03-023-30
I	Tertiary crushing line discharge conveyor	3-03-023-31
J	Screening	3-03-023-03
K	Grinder feed	3-03-023-34
L	Primary grinding	3-03-023-06
M	Classification	3-03-023-36
N	Magnetic separation	3-03-023-17
O	Secondary grinding	3-03-023-38
P	Conveyor transfer to concentrator	3-03-023-41
Q	Concentrate storage	3-03-023-44
R	Bentonite storage	3-03-023-07
S	Bentonite transfer to blending	3-03-023-45
T	Bentonite blending	3-03-023-08
U	Green pellet screening	3-03-023-47
V	Chip regrinding	3-03-023-11
W	Grate/kiln furnace feed	3-03-023-49
X	Straight grate furnace feed	3-03-023-79
Y	Vertical shaft furnace feed	3-03-023-69
Z	Hearth layer feed to furnace	3-03-023-48
AA	Grate/kiln, gas-fired, acid pellets	3-03-023-51
AB	Grate/kiln, gas-fired, flux pellets	3-03-023-52
AC	Grate/kiln, gas- and oil-fired, acid pellets	3-03-023-53
AD	Grate/kiln, gas- and oil-fired, flux pellets	3-03-023-54
AE	Grate/kiln, coke-fired, acid pellets	3-03-023-55
AF	Grate/kiln, coke-fired, flux pellets	3-03-023-56
AG	Grate/kiln, coke- and coal-fired, acid pellets	3-03-023-57
AH	Grate/kiln, coke- and coal-fired, flux pellets	3-03-023-58
AI	Grate/kiln, coal-fired, acid pellets	3-03-023-59
AJ	Grate/kiln, coal-fired, flux pellets	3-03-023-60

TABLE 11.23-1. (continued)

Key	Source	SCC
AK	Grate/kiln, coal- and oil-fired, acid pellets	3-03-023-61
AL	Grate/kiln, coal- and oil-fired, flux pellets	3-03-023-62
AM	Vertical shaft, gas-fired, top gas stack, acid pellets	3-03-023-71
AN	Vertical shaft, gas-fired, top gas stack, flux pellets	3-03-023-72
AO	Vertical shaft, gas-fired, bottom gas stack, acid pellets	3-03-023-73
AP	Vertical shaft, gas-fired, bottom gas stack, flux pellets	3-03-023-74
AQ	Straight grate, gas-fired, acid pellets	3-03-023-81
AR	Straight grate, gas-fired, flux pellets	3-03-023-82
AS	Straight grate, oil-fired, acid pellets	3-03-023-83
AT	Straight grate, oil-fired, flux pellets	3-03-023-84
AU	Straight grate, coke-fired, acid pellets	3-03-023-85
AV	Straight grate, coke-fired, flux pellets	3-03-023-86
AW	Straight grate, coke- and gas-fired, acid pellets	3-03-023-87
AX	Straight grate, coke- and gas-fired, flux pellets	3-03-023-88
AY	Grate/kiln furnace discharge	3-03-023-50
AZ	Vertical shaft furnace discharge	3-03-023-70
BA	Straight grate furnace discharge	3-03-023-80
BB	Hearth layer screen	3-03-023-93
BC	Pellet cooler	3-03-023-15
BD	Pellet screen	3-03-023-95
BE	Pellet transfer to storage	3-03-023-16
BF	Pellet storage bin loading	3-03-023-96
BG	Secondary storage bin loading	3-03-023-97
BH	Tertiary storage bin loading	3-03-023-98
b	Haul road, rock	3-03-023-21
b	Haul road, taconite	3-03-023-22
b	Nonmagnetic separation	3-03-023-18
b	Tailings basin	3-03-023-40
b	Other, not classified	3-03-023-99
c	Traveling grate feed	3-03-023-09
c	Traveling grate discharge	3-03-023-10
c	Indurating furnace: gas-fired	3-03-023-12
c	Indurating furnace: oil-fired	3-03-023-13
c	Indurating furnace: coal-fired	3-03-023-14
c	Kiln	3-03-023-19
c	Conveyors, transfer, and loading	3-03-023-20

^aRefers to labels in Figure 2-1.

^bNot shown in Figure 2-1.

^cInactive code.

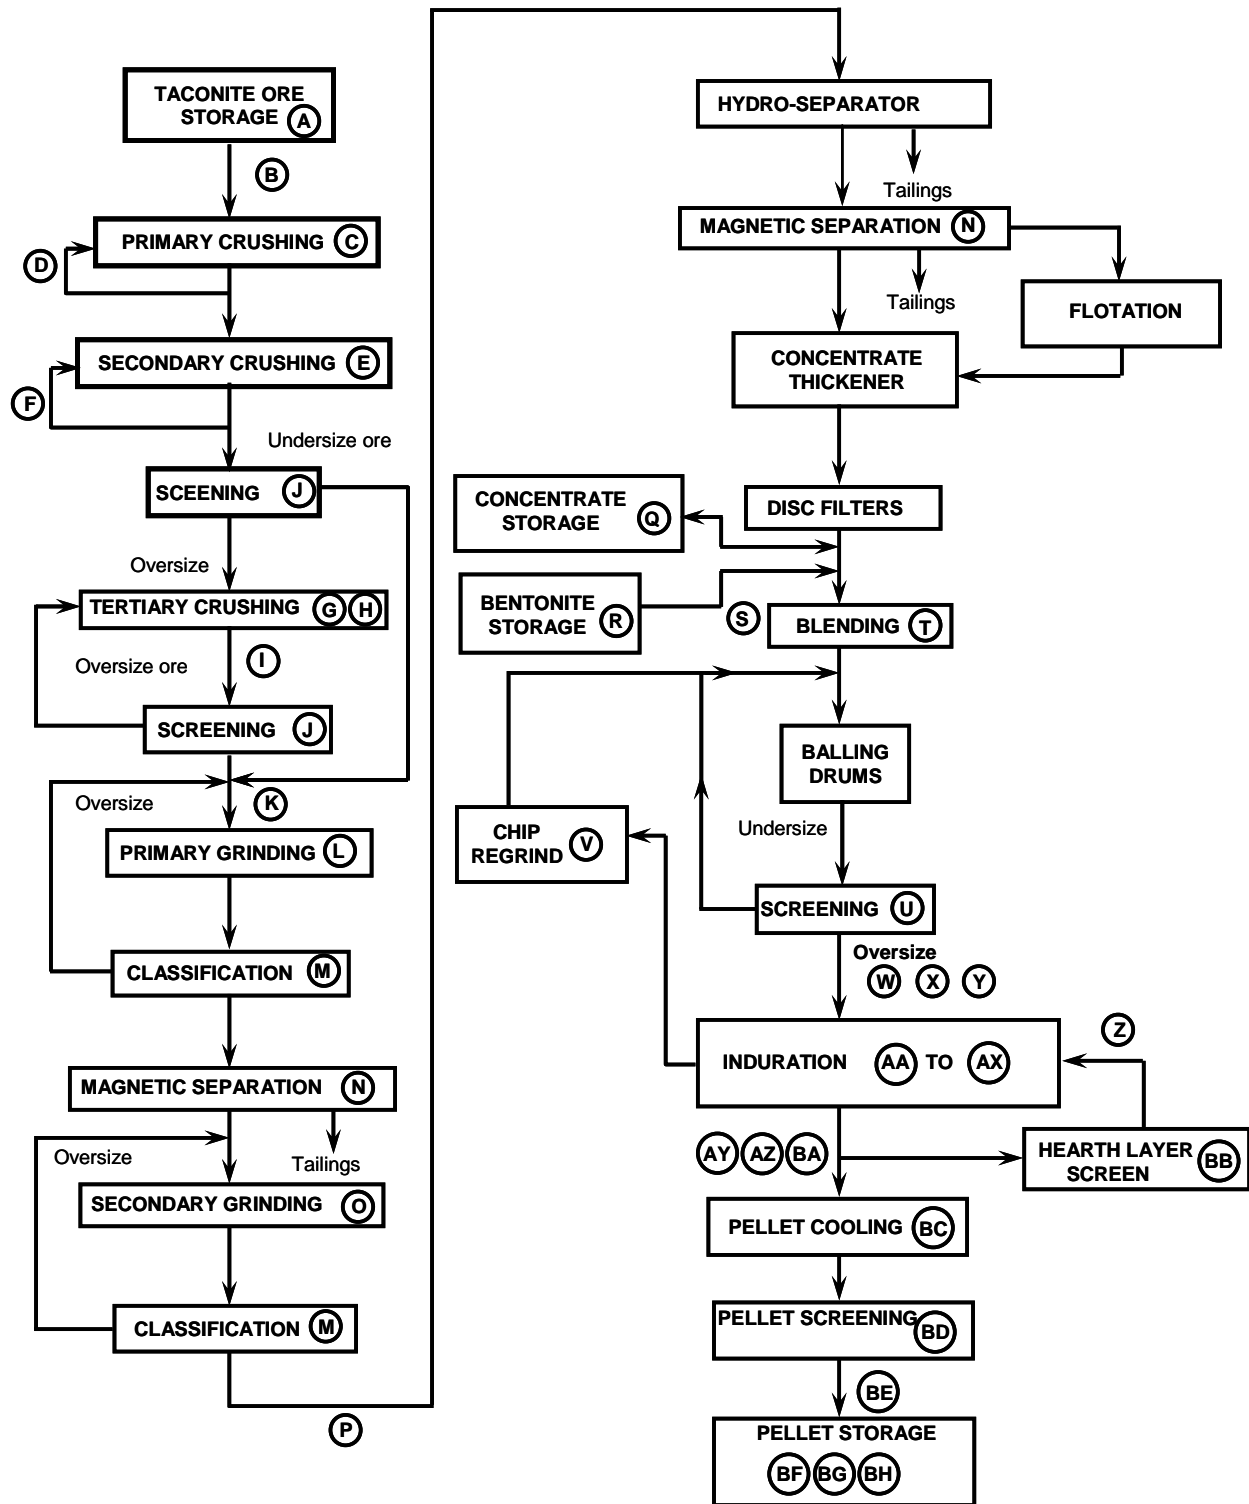


Figure 11.23 - 1. Process flow diagram for taconite ore processing.
(Refer to Table 11.23-1 for Source Classification Codes)

Crude ores in which most of the recoverable iron is magnetite (or, in rare cases, maghemite) are normally concentrated by magnetic separation. The crude ore may contain 30 to 35 percent total iron by assay, but theoretically only about 75 percent of this is recoverable magnetite. The remaining iron is discarded with the gangue.

Nonmagnetic taconite ores are concentrated by froth flotation or by a combination of selective flocculation and flotation. The method is determined by the differences in surface activity between the iron and gangue particles. Sharp separation is often difficult.

Various combinations of magnetic separation and flotation may be used to concentrate ores containing various iron minerals (magnetite and hematite, or maghemite) and wide ranges of mineral grain sizes. Flotation is also often used as a final polishing operation on magnetic concentrates.

Pelletization is the third major step in taconite ore processing. Iron ore concentrates must be coarser than about No. 10 mesh to be acceptable as blast furnace feed without further treatment. Finer concentrates are agglomerated into small "green" pellets, which are classified as either acid pellets or flux pellets. Acid pellets are produced from iron ore and a binder only, and flux pellets are produced by adding between 1 and 10 percent limestone to the ore and binder before pelletization. Pelletization generally is accomplished by tumbling moistened concentrate with a balling drum or balling disc. A binder, usually powdered bentonite, may be added to the concentrate to improve ball formation and the physical qualities of the "green" balls. The bentonite is mixed with the carefully moistened feed at 5 to 10 kilograms per megagram (kg/Mg) (10 to 20 pounds per ton [lb/ton]).

The pellets are hardened by a procedure called induration. The green balls are dried and heated in an oxidizing atmosphere at incipient fusion temperature of 1290° to 1400°C (2350° to 2550°F), depending on the composition of the balls, for several minutes and then cooled. The incipient fusion temperature for acid pellets falls in the lower region of this temperature range, and the fusion temperature for flux pellets falls in the higher region of this temperature range. The three general types of indurating apparatus currently used are the vertical shaft furnace, the straight grate, and the grate/kiln. Most large plants and new plants use the grate/kiln. Currently, natural gas is the most common fuel used for pellet induration, but heavy oil is used at a few plants, and coal and coke may also be used.

In the vertical shaft furnace, the wet green balls are distributed evenly over the top of the slowly descending bed of pellets. A stream of hot gas of controlled temperature and composition rises counter to the descending bed of pellets. Auxiliary fuel combustion chambers supply hot gases midway between the top and bottom of the furnace.

The straight grate furnace consists of a continuously moving grate, onto which a bed of green pellets is deposited. The grate passes through a firing zone of alternating up and down currents of heated gas. The fired pellets are cooled either on an extension of the grate or in a separate cooler. An important feature of the straight grate is the "hearth layer", which consists of a 10- to 15-centimeter (4- to 6-inch) thick layer of fired pellets that protects the grate. The hearth layer is formed by diverting a portion of the fired pellets exiting the firing zone of the furnace to a hearth layer screen, which removes the fines. These pellets then are conveyed back to the feed end of the straight grate and deposited on to the bare grate. The green pellets being fed to the furnace are deposited on the hearth layer prior to the burning zone of the furnace.

The grate/kiln apparatus consists of a continuous traveling grate followed by a rotary kiln. The grate/kiln product must be cooled in a separate cooler, usually an annular cooler with counter current airflow.

11.23.3 Emissions And Controls^{2-7,41}

Particulate matter (PM) emission sources in taconite ore processing plants are indicated in Figure 11.23-1. Taconite ore is handled dry through the initial stages of crushing and screening. All crushers, size classification screens, and conveyor transfer points are major points of PM emissions. Crushed ore is normally wet ground in rod and ball mills. Because the ore remains wet, PM emissions are insignificant for the rest of the process until the drying stage of induration. A few plants use dry autogenous or semi-autogenous grinding and have higher emissions than do conventional plants.

Emissions from crushing and conveying operations are generally controlled by a hood-and-duct system that leads to a cyclone, rotoclone, multiclone, scrubber, or fabric filter. The inlet of the control device will often be fed by more than one duct. Water sprays are also used to control emissions.

The first source of emissions in the pelletizing process is the transfer and blending of bentonite. Additional emission points in the pelletizing process include the main waste gas stream from the indurating furnace, pellet handling, furnace transfer points (grate feed and discharge), and annular coolers for plants using the grate/kiln furnace.

Induration furnaces generate sulfur dioxide (SO₂). The SO₂ originates both from the fuel and the raw material (concentrate, binder, and limestone). Induration furnaces also emit combustion products such as nitrogen oxides (NO_x), and carbon monoxide (CO). Because of the additional heating requirements, emissions of NO_x and SO₂ generally are higher when flux pellets are produced than when acid pellets are produced.

The combination of multicyclones and wet scrubbers is a common configuration for controlling furnace waste gas. The purpose of the multicyclones is to recover material from the drying gases as they pass from the preheat stage to the drying stage. The wet scrubber reduces concentrations of SO₂ and PM in the furnace waste gas. Minor emission sources, such as grate feed and discharge, are usually controlled by small wet scrubbers.

Annular coolers normally operate in stages. The exhaust of the first-stage cooler is vented to the indurating furnace as preheated combustion gas. The second and third stages generally are uncontrolled.

Particulate matter emissions also arise from ore mining operations. The largest source of PM in taconite ore mines is traffic on unpaved haul roads. Other significant PM emission sources at taconite mines are tailing basins and wind erosion. Although blasting is a notable emission source of the various fractions of PM, it is a short-term event, and most of the material settles quickly.

Emissions from taconite ore processing facilities constructed or modified after August 24, 1982 are regulated under 40 CFR 60, subpart LL, Standards of Performance for Metallic Mineral Processing Plants. The affected emission sources include crushers, screens, conveyors, conveyor transfer points, storage bins, enclosed storage areas, product packaging stations, and truck and rail loading and unloading stations. The regulation limits PM stack emissions from these sources to 0.05 grams per dry standard cubic meter (0.022 grains per dry standard cubic foot). In addition, the opacity of stack emissions for these sources is limited to 7 percent unless the stack is equipped with a wet scrubber, and process fugitive emissions are limited to 10 percent. The standard does not affect emissions from indurating furnaces.

Table 11.23-2 presents the factors for PM emissions from taconite ore indurating furnaces. Factors for emissions of PM from taconite ore processing sources other than furnaces are presented in Table 11.23-3. Factors for emissions of SO₂, NO_x, CO, and CO₂ from taconite ore processing are presented in Tables 11.23-4 and 11.23-5 for acid pellet and flux pellet production, respectively. Table 11.23-6 presents emission factors for other pollutants emitted from taconite ore indurating furnaces. Emission factors for fugitive dust sources associated with taconite ore processing can be estimated using the predictive equations found in Section 13.2 of AP-42, which includes, for the parameters used in the equations, values based on measurements at taconite ore processing facilities.

Table 11.23-2. EMISSION FACTORS FOR TACONITE ORE INDURATING FURNACES^a

Source	Filterable ^b				Condensable ^c	EMISSION FACTOR RATING
	PM	EMISSION FACTOR RATING	PM-10	EMISSION FACTOR RATING		
Natural gas-fired grate/kiln (SCC 3-03-023-51,-52)	7.4 ^d	D	0.63 ^e	E	0.022 ^f	D
Natural gas-fired grate/kiln, with multiclone (SCC 3-03-023-51,-52)	0.44 ^g	D	0.13 ^h	E	NA	
Natural gas-fired grate/kiln, with wet scrubber (SCC 3-03-023-51,-52)	0.082 ^j	C	ND		0.0055 ^k	D
Natural gas/oil-fired grate/kiln (SCC 3-03-023-53,-54)	ND		ND		0.040 ^m	D
Natural gas/oil-fired grate/kiln, with ESP (SCC 3-03-023-53,-54)	0.017 ^m	E	ND		ND	
Coal/oil-fired grate/kiln, with wet scrubber (SCC 3-03-023-61,-62)	0.19 ⁿ	E	ND		ND	
Coke-fired grate/kiln, with wet scrubber (SCC 3-03-023-55,-56)	0.10 ^p	E	ND		ND	
Coke/coal-fired grate/kiln, with wet scrubber (SCC 3-03-023-57,-58)	0.14 ^q	D	ND		ND	
Gas-fired vertical shaft top gas stack (SCC 3-03-023-71,-72)	16 ^r	D	ND		ND	
Gas-fired vertical shaft top gas stack, with multiclone (SCC 3-03-023-71,-72)	1.4 ^s	D	ND		ND	
Gas-fired vertical shaft top gas stack, with wet scrubber (SCC 3-03-023-71,-72)	0.92 ^t	E	ND		0.050 ^t	E
Gas-fired vertical shaft top gas stack, with multiclone and wet scrubber (SCC 3-03-023-71,-72)	0.66 ^u	D	ND		ND	
Gas-fired vertical shaft bottom gas stack, with rotoclone (SCC 3-03-023-73,-74)	0.031 ^t	E	ND		0.0086 ^t	E
Oil-fired straight grate (SCC 3-03-023-83,-84)	1.2 ^v	E	ND		ND	
Coke/gas-fired straight grate, with wet scrubber (SCC 3-03-023-88)*	0.11 ^w	D	ND		ND	

Table 11.23-2 (cont.).

^aApplicable to both acid pellets and flux pellets. Emission factors in units of lb/ton of fired pellets produced. One lb/ton is equivalent to 0.5 kg/Mg. Factors represent uncontrolled emissions unless noted. SCC = Source Classification Code. ND = no data.

^bFilterable PM is that PM collected on or prior to the filter of an EPA Method 5 sampling train or equivalent.

^cCondensable PM is that PM collected in the impinger portion of a PM sampling train.

^dReferences 4-5,40.

^eReference 40.

^fReferences 4,36,39-40. Based on data presented in Reference 40, 84 percent of condensibles consists of inorganic material.

^gReferences 32-36,39,42-43.

^hReference 39.

ⁱReferences 20,27,37.

^kReferences 4,37.

^mReference 5.

ⁿReference 18.

^pReference 29.

^qReferences 26-27.

^rReferences 12-14,24.

^sReferences 12-13,24.

^tReference 45.

^uReference 14.

^vReference 6.

^wReferences 30-31.

*NOTE (SCC 3-03-023-83,-84) was corrected to (SCC 3-03-023-88) September 27, 2012

Table 11.23-3. EMISSION FACTORS FOR TACONITE ORE PROCESSING—
OTHER SOURCES^a

Source	Filterable ^b				Condensable ^c	EMISSION FACTOR RATING
	PM	EMISSION FACTOR RATING	PM-10	EMISSION FACTOR RATING		
Primary crusher, with cyclone (SCC 3-03-023-01)	0.25 ^d	E	ND		ND	
Primary crusher, with cyclone and multiclone (SCC 3-03-023-01)	0.060 ^d	E	ND		ND	
Primary crusher, with wet scrubber (SCC 3-03-023-01)	0.0012 ^e	E	ND		ND	
Primary crusher, with fabric filter (SCC 3-03-023-01)	0.0019 ^f	E	ND		ND	
Secondary crushing line, with wet scrubber (SCC 3-03-023-27)	0.0027 ^g	E	ND		ND	
Tertiary crusher, with rotoclone (SCC 3-03-023-02)	0.0013 ^h	E	ND		ND	
Tertiary crushing line, with wet scrubber (SCC 3-03-023-30)	0.0016 ^g	D	ND		ND	
Grinder feed, with wet scrubber (SCC 3-03-023-34)	0.0011 ⁱ	C	ND		ND	
Hearth layer feed, with wet scrubber (SCC 3-03-023-48)	0.017 ^k	D	ND		ND	
Hearth layer screen, with wet scrubber (SCC 3-03-023-93)	0.038 ^m	E	ND		ND	
Grate/kiln feed, with wet scrubber (SCC 3-03-023-49)	6.6 x 10 ^{-5(g)}	E	ND		ND	
Grate/kiln discharge (SCC 3-03-023-50)	0.82 ⁿ	D	ND		0.00035 ^p 9.0 x 10 ^{-5 (q)}	E E
Grate/kiln discharge, with wet scrubber (SCC 3-03-023-50)	0.0019 ^f	E	ND		0.00012 ^q	E
Straight grate feed (SCC 3-03-023-79)	0.63 ^s	E	ND		ND	
Straight grate discharge (SCC 3-03-023-80)	1.4 ^s	E	ND		ND	
Straight grate discharge, with wet scrubber (SCC 3-03-023-80)	0.012 ^k	D	ND		ND	

Table 11.23-3. EMISSION FACTORS FOR TACONITE ORE PROCESSING—
OTHER SOURCES^a (cont.)

Source	Filterable ^b				Condensable ^c	EMISSION FACTOR RATING
	PM	EMISSION FACTOR RATING	PM-10	EMISSION FACTOR RATING		
Pellet screen (SCC 3-03-023-95)	10 ^u	E	ND		ND	
Pellet screen, with rotoclone (SCC 3-03-023-95)	0.037 ^u	E	ND		ND	
Primary crusher return conveyor transfer, with wet scrubber (SCC 3-03-023-25)	0.00031 ^f	E	ND		ND	
Pellet transfer to storage, with wet scrubber (SCC 3-03-023-16)	0.0036 ^m	E	ND		ND	
Secondary crusher return conveyor transfer, with wet scrubber (SCC 3-03-023-28)	0.0057 ^v	D	ND		ND	
Conveyor transfer to concentrator, with wet scrubber (SCC 3-03-023-41)	0.00028 ^g	E	ND		ND	
Tertiary crushing line discharge conveyor, with wet scrubber (SCC 3-03-023-31)	0.0017 ^g	E	ND		ND	
Bentonite storage bin loading, with wet scrubber (SCC 3-03-023-07)	2.4 ^m	E	ND		ND	
Bentonite transfer (SCC 3-03-023-45)	3.2 ^s	E	ND		ND	
Bentonite transfer, with wet scrubber (SCC 3-03-023-45)	0.11 ^s	E	ND		ND	
Bentonite blending (SCC 3-03-023-08)	19 ^s	E	ND		ND	
Bentonite blending, with wet scrubber (SCC 3-03-023-08)	0.25 ^s	E	ND		ND	
Bentonite blending, with fabric filter (SCC 3-03-023-08)	0.11 ^s	E	ND		ND	
Pellet storage bin loading (SCC 3-03-023-96)	3.7 ^u	E	ND		ND	
Pellet storage bin loading, with rotoclone (SCC 3-03-023-96)	0.071 ^u	E	ND		ND	

Table 11.23-3. EMISSION FACTORS FOR TACONITE ORE PROCESSING—
OTHER SOURCES^a (cont.)

Source	Filterable ^b				Condensible ^c	EMISSION FACTOR RATING
	PM	EMISSION FACTOR RATING	PM-10	EMISSION FACTOR RATING		
Tertiary storage bin loading, with wet scrubber (SCC 3-03-023-98)	0.0018 ^g	D	ND		ND	

^aFactors represent uncontrolled emissions unless noted. Emission factors for furnace feed, furnace discharge, coolers, and product handling are in units of lb/ton of pellets produced; emission factors for other sources are in units of lb/ton of material processed or handled. One lb/ton is equivalent to 0.5 kg/Mg. SCC = Source Classification Code. ND = no data available.

^bFilterable PM is that PM collected on or prior to the filter of an EPA Method 5 (or equivalent) sampling train.

^cCondensable PM is that PM collected in the impinger portion of a PM sampling train.

^dReferences 10-11.

^eReference 22.

^fReference 27.

^gReference 28.

^hReference 6.

ⁱReferences 7,9.

^kReferences 8-9.

^mReference 8.

ⁿReferences 4-5.

^pReference 5.

^qReference 4. Condensable inorganic PM fraction only.

^rReference 4.

^sReference 2.

^tReferences 16-17,27.

^uReference 23.

^vReferences 21,28.

Table 11.23-4. EMISSION FACTORS FOR TACONITE ORE INDURATING FURNACES--
ACID PELLETT PRODUCTION^a

Source	SO ₂ ^b	EMISSION FACTOR RATING	NO _x	EMISSION FACTOR RATING	CO	EMISSION FACTOR RATING	CO ₂ ^c	EMISSION FACTOR RATING
Natural gas-fired grate/kiln (SCC 3-03-023-51)	0.29 ^d	D	1.5 ^e	D	0.014 ^f	D	99 ^g	C
Natural gas-fired grate/kiln, with wet scrubber (SCC 3-03-023-51)	0.053 ^h	D	j		j		j	
Coke-fired grate/kiln (SCC 3-03-023-55)	1.9 ^k	E	ND		ND		99 ^g	C
Coal/coke-fired grate/kiln, (SCC 3-03-023-57)	2.3 ^m	E	ND		ND		99 ^g	C
Coal/coke-fired grate/kiln, with wet scrubber (SCC 3-03-023-57)	1.5 ⁿ	D	ND		ND		j	
Gas-fired vertical shaft top gas stack (SCC 3-03-023-71)	ND		0.20 ^p	E	0.077 ^p	E	94 ^q	C
Gas-fired vertical shaft top gas stack, with wet scrubber (SCC 3-03-023-71)	0.28 ^p	E	j		j		j	
Gas-fired straight grate (SCC 3-03-023-81)	ND		ND		0.039 ^f	E	ND	
Gas-fired straight grate, with wet scrubber (SCC 3-03-023-81)	0.10 ^f	E	ND		j		ND	
Coke-fired straight grate, with multiclone and wet scrubber (SCC 3-03-023-85)	0.99 ^s	D	ND		j		ND	
Coke/gas-fired straight-grate (SCC 3-03-023-87)	ND		0.44 ^f	D	0.15 ^f	E	62 ^s	D

^aEmission factors in units of lb/ton of fired pellets produced. One lb/ton is equivalent to 0.5 kg/Mg. Factors represent uncontrolled emissions unless noted. SCC = Source Classification Code. ND = no data.

^bMass balance of sulfur may yield a more representative emission factor for a specific facility than the SO₂ factors presented in this table.

^cMass balance on carbon may yield a more representative emission factor for a specific facility than the CO₂ factors represented in this table.

^dReferences 4,39-40.

^eReferences 19,27,39.

^fReference 39.

^gReferences 5,18,29,32-34,39-40,42.

^hReference 4.

ⁱSee emission factor for uncontrolled emissions.

^kReference 29.

^mReference 15.

ⁿReferences 15,25,29.

^pReference 44.

^qReferences 12-14,24,44-45.

^rReference 31.

^sReferences 30-31.

Table 11.23-5. EMISSION FACTORS FOR TACONITE ORE INDURATING FURNACES--
FLUX PELLETT PRODUCTION^a

Source	SO ₂ ^b	EMISSION FACTOR RATING	NO _x	EMISSION FACTOR RATING	CO	EMISSION FACTOR RATING	CO ₂ ^c	EMISSION FACTOR RATING
Natural gas-fired grate/kiln, with wet scrubber (SCC 3-03-023-52)	0.14 ^d	D	1.5 ^e	D	0.10 ^f		130 ^g	C
Coal/coke-fired grate/kiln, with wet scrubber (SCC 3-03-023-58)	1.5 ^h	D	ND		ND		130 ^g	C
Gas-fired straight grate (SCC 3-03-023-82)	ND		2.5 ^j	D	ND		ND	
Pellet cooler (SCC 3-03-023-15)	Neg.		ND		ND		6.4 ^f	E

^aEmission factors in units of lb/ton of fired pellets produced. One lb/ton is equivalent to 0.5 kg/Mg. Factors represent uncontrolled emissions unless noted. SCC = Source Classification Code. ND = no data. Neg. = negligible.

^bMass balance of sulfur may yield a more representative emission factor for a specific facility than the SO₂ factors presented in this table.

^cMass balance on carbon may yield a more representative emission factor for a specific facility than the CO₂ factors represented in this table.

^dReference 20.

^eReferences 19,27,39.

^fReference 27.

^gReferences 20,25-27,36-37.

^hReferences 15,25,29.

^jReference 38.

Table 11.23-6. EMISSION FACTORS FOR TACONITE ORE PROCESSING--
OTHER POLLUTANTS^a

EMISSION FACTOR RATING: E

Source	Pollutant	Emission factor, lb/ton	References
Gas-fired grate/kiln (SCC 3-03-023-51,-52)	VOC	0.0037 ^b 0.075 ^c	39 27
Gas-fired grate/kiln, with multiclone (SCC 3-03-023-51,-52)	Lead	0.00050	39
Coke-fired grate/kiln (SCC 3-03-023-55,-56)	H ₂ SO ₄	0.17	29
Coke-fired grate/kiln, with wet scrubber (SCC 3-03-023-55,-56)	H ₂ SO ₄	0.099	29
Gas-fired vertical shaft top gas stack (SCC 3-03-023-71,-72)	VOC	0.013 ^d	44
Gas-fired vertical shaft bottom gas stack (SCC 3-03-023-73,-74)	VOC	0.046 ^d	44
Gas-fired straight grate furnace, with multiclone and wet scrubber (SCC 3-03-023-81,-82)	Lead	6.8 x 10 ⁻⁵	31
Gas-fired straight grate furnace, with multiclone and wet scrubber (SCC 3-03-023-85,-86)	Beryllium	2.2 x 10 ⁻⁷	31
Coke/gas-fired straight grate furnace, with multiclone and wet scrubber (SCC 3-03-023-87,-88)	Lead	7.6 x 10 ⁻⁵	31
Coke/gas-fired straight grate furnace, with multiclone and wet scrubber (SCC 3-03-023-87,-88)	Beryllium	2.9 x 10 ⁻⁷	31

^aFactors represent uncontrolled emissions unless noted. All emission factors for furnaces in lb/ton of fired pellets produced. One lb/ton is equivalent to 0.5 kg/Mg. SCC = Source Classification Code. ND = no data available.

^bBased on Method 25A data. EMISSION FACTOR RATING: D.

^cBased on Method 25 data.

^dBased on Method 25A data.

REFERENCES FOR SECTION 11.23

1. C.M. Cvetic and P.H. Kuck, "Iron Ore", in: *Minerals Yearbook, Vol. I*, U. S. Government Printing Office, 1991, pp. 521-547.
2. J. P. Pilney and G. V. Jorgensen, *Emissions From Iron Ore Mining, Beneficiation And Pelletization, Volume 1*, EPA Contract No. 68-02-2113, Midwest Research Institute, Minnetonka, MN, June 1983.
3. A. K. Reed, *Standard Support And Environmental Impact Statement For The Iron Ore Beneficiation Industry (Draft)*, EPA Contract No. 68-02- 1323, Battelle Columbus Laboratories, Columbus, OH, December 1976.
4. *Air Pollution Emissions Test, Eveleth Taconite, Eveleth, MN*, EMB 76-IOB-3, U. S. Environmental Protection Agency, Research Triangle Park, NC, November 1975.

5. *Air Pollution Emission Test, Empire Mining Company, Palmer, MI, EMB 76-IOB-2, U. S. Environmental Protection Agency, Research Triangle Park, NC, November 1975.*
6. *Emission Testing Report, Reserve Mining Company, Silver Bay, MN, EMB 74-HAS-1, U. S. Environmental Protection Agency, Research Triangle Park, NC, June 1974.*
7. *Results Of The January 1977 Particulate Emission Testing Of Crusher Feed Mill Scrubbers Nos. 2, 3, 5, And 6 Conducted At The Hibbing Taconite Company, Hibbing, MN, Interpoll, Inc., St. Paul, MN, June 8, 1977.*
8. *Results Of The June 27-July 1, 1977 Particulate Emission Tests Conducted On Selected Sources In The Pelletizer Building At The Hibbing Taconite Company Plant, Hibbing, MN, Interpoll, Inc., St. Paul, MN, August 16, 1977.*
9. *Phase II Particulate Emissions Compliance Testing, Hibbing Taconite Company, Hibbing, MN, September 4-6, 1979.*
10. *Results Of The March 15, 1990 Dust Collector Performance Test On The No. 1 Crusher Primary Dust Collector At The Cyprus Northshore Mining Facility In Babbitt, MN, Interpoll Laboratories, Inc., Circle Pines, MN, April 19, 1990.*
11. *Results Of The March 9, 1990 Dust Collector Performance Test On The No. 1 Crusher Secondary Collector At The Cyprus Northshore Mining Facility In Babbitt, MN, Interpoll Laboratories, Inc., Circle Pines, MN, April 18, 1990.*
12. *Results Of The May 22 And 23, 1984, Dust Collection Efficiency Tests On The D-2 And E-2 Furnace Top Gas Mechanical Collectors At The Erie Mining Company Pellet Plant Near Hoyt Lakes, MN, Interpoll, Inc., Circle Pines, MN, May 29, 1984.*
13. *Results Of The December 17, 1981 Compliance Test On The D-2 Furnace Dust Control System At The Erie Mining Company Pellet Plant Near Hoyt Lakes, MN, Interpoll, Inc., St. Paul, MN, December 22, 1981.*
14. *Results Of The February 20, 1980 Particulate Emission Test On The D-1 Furnace Top Gas Wet Collector At The Erie Mining Company Plant Near Hoyt Lakes, MN, Interpoll, Inc., St. Paul, MN, March 4, 1980.*
15. *Results of the October 12-15, 1987 Air Emission Compliance Tests At The Eveleth Taconite Plant in Eveleth, MN, Interpoll Laboratories, Inc., Circle Pines, MN, December 18, 1987.*
16. *Results Of The July 9, 1981 Particulate Emission Compliance Test On The Kiln Cooler Exhaust Stack At Eveleth Mines, Eveleth, MN, Interpoll Laboratories, Inc., St. Paul, MN, July 22, 1981.*
17. *Results Of The March 11, 1980 Particulate Emission Compliance Test On The Kiln Cooler Exhaust Stack At Eveleth Mines, Eveleth, MN, Interpoll, Inc., St. Paul, MN, April 18, 1980.*
18. *Results Of The December 13 And 14, 1979 Particulate Emission Compliance Tests On The Kiln Cooler Exhaust And The 2A Waste Gas Stacks At The Eveleth Expansion Company Plant Near Eveleth, MN, Interpoll, Inc., St. Paul, MN, January 22, 1980.*

19. *Results Of The June 12, 1975 Oxides Of Nitrogen Determinations At The Fairlane Plant Pellet Furnace Wet Scrubber Inlet And Outlet*, Eveleth Taconite Company, Eveleth, MN, Interpoll, Inc., St. Paul, MN, June 30, 1975.
20. *Results Of The March/April 1992 Emission Performance Tests On The Nos. 4 And 5 Scrubber Stacks At The USS Minnesota Ore Operations Facility In Mountain Iron, MN*, Interpoll Laboratories, Inc., Circle Pines, MN, April 23, 1992.
21. *Results Of The February 18 And 19, 1992 Particulate Emission Performance Testing On Two SEI Multiple Throat Venturi Type Wet Scrubber Systems At The USS Minnesota Ore Operations Facility, Mountain Iron, MN*, Interpoll Laboratories, Inc., Circle Pines, MN, March 11, 1992.
22. *Crusher Environereing Wet Scrubber Dust Collectors Particulate Emissions Compliance Testing Hibbing Taconite Company*, Hibbing, MN, October 18, 1982.
23. *Results Of The June 25 And 26, 1980 Particulate Emission Compliance Tests On The No. 2 Loading Pocket Collector And The Nos. 7 And 8 Pellet Screen Collector At The Erie Mining Company Plant Near Hoyt Lakes, MN*, Interpoll, Inc., St. Paul, MN, July 7, 1980.
24. *Results Of The June 12-15, 1984, Dust Collection Efficiency Tests On The D-2 And E-2 Furnace Top Gas Mechanical Collectors At The Erie Mining Company Pellet Plant Near Hoyt Lakes, MN*, Interpoll, Inc., Circle Pines, MN, June 22, 1984.
25. *Results Of The August 6, 1991 SO₂ Emission Engineering Tests At The USX Minnesota Ore Operation Facility In Mountain Iron, MN*, Interpoll Laboratories, Inc., Circle Pines, MN, August 15, 1991.
26. *Results Of The January 25, 1990 Particulate And Sulfur Dioxide Engineering Emission Test On The Line 7 Grate Kiln At The USX Minnesota Ore Operation Facility, Mountain Iron, MN*, Interpoll Laboratories, Inc., Circle Pines, MN, March 7, 1990.
27. *Results Of The March 28-31, 1989 Air Emission Compliance Testing At The USS Plant in Mountain Iron, MN*, Interpoll Laboratories, Inc., Circle Pines, MN, April 21, 1989.
28. *Results Of The January 8-10, 1980 Particulate Emission Compliance Tests On Emission Source Nos. 6.39, 6.40, 6.34, 6.44, 6.41, 6.56, 6.43, 8.43, 8.47, And 8.49 At The U.S. Steel Minntac Plant In Mountain Iron, MN*, Interpoll, Inc., St. Paul, MN, February 8, 1980.
29. *Results Of The May 21 And 22, 1987 Particulate And SO₂/SO₃ Emission Compliance Tests On The Line 2 Induration Furnace Waste Gas Systems At The Eveleth Taconite Plant In Eveleth, MN*, Interpoll Inc., Circle Pines, MN, June 25, 1987.
30. *Results Of The August 6-8, 1986, Particulate And SO₂ Compliance Tests On The Indurating Gas Wet Scrubber Stacks At The Inland Steel Mining Company In Virginia, MN*, Interpoll Inc., Circle Pines, MN, August 19 1986.
31. *Results Of The May 5-7, 1987, Atmospheric Emission Tests On The Induration Furnaces At The Hibbing Taconite Company In Hibbing, MN*, Interpoll, Inc., Circle Pines, MN, May 14, 1987.
32. *Particulate Emissions Testing For National Steel Pellet Company, Keewatin, MN, Waste Gas Stack No. 2B*, June 17, 1992, Shell Engineering and Associates, Inc., Columbia, MO, July 17, 1992.

33. *Particulate Emissions Testing For National Steel Pellet Company*, Keewatin, MN, Waste Gas Stack No. 2A, June 5, 1991, Shell Engineering and Associates, Inc. Columbia, MO, June 28, 1991.
34. *Particulate Emissions Testing For National Steel Pellet Company*, Keewatin, MN, Waste Gas Stack No. 2B, May 16, 1990, Shell Engineering and Associates, Inc., Columbia, MO, May 30, 1990.
35. *Particulate Emissions Testing For National Steel Pellet Company*, Keewatin, MN, Waste Gas Stack No. 2A, June 7, 1989, Shell Engineering and Associates, Inc., Columbia, MO, June 14, 1989.
36. *Results Of The October 13, 1994 National Steel Pellet Company Particulate And Visible Waste Gas Stack 2B Emissions Compliance Test*, Barr Engineering Company, Minneapolis, MN, November 1994.
37. *Results Of The April 28, 1993 State Air Emission Compliance Testing On The No. 4 And 5 Pelletizers At The U.S. Steel Plant In Mountain Iron, MN*, Interpoll Laboratories, Inc., Circle Pines, MN, June 10, 1993.
38. *Results Of The July 31 And August 1, 1990 NO_x Emission Compliance Test On The Flux Pellet Induration Furnace At The Inland Steel Mining Plant*, Interpoll Laboratories, Inc., Circle Pines, MN, October 10, 1990.
39. *Results Of The September 12, 16, 23, And October 12, 1994 National Steel Pellet Company Waste Gas Stack 2B Emission Tests*, Barr Engineering Company, Minneapolis, MN, November 1994.
40. *Results Of The March 25, 1994 Air Emission Engineering Tests On The No. 3 Waste Gas Stack At The U.S. Steel Plant In Mountain Iron, Minnesota*, Interpoll Laboratories, Inc., Circle Pines, MN, April 1994.
41. Written communication from P. O'Neill, Minnesota Pollution Control Association, Minneapolis, MN, to R. E. Myers, U. S. Environmental Protection Agency, Research Triangle Park, NC, June 20, 1996.
42. *Results of the June 22, 1993 Particulate And Opacity Compliance Tests Conducted On The No. 2A Waste Gas Stack At The National Steel Pellet Plant In Keewatin, Minnesota*, Interpoll Laboratories, Inc., Circle Pines, MN, July 26, 1993.
43. *Results Of The June 6, 1995 National Steel Pellet Company Particulate Emission Compliance Test Waste Gas Stack 2A (Emission Point 30)*, Barr Engineering Company, Minneapolis, MN, June 1995.
44. Written Communication from D. Koschak, LTV Steel Mining Company, Hoyt Lakes, MN, to S. Arkley, Minnesota Pollution Control Association, Minneapolis, MN. October 31, 1995.
45. *Results Of The July 11-13, 1995 State Air Emission Performance Testing At The LTV Steel Mining Plant Company Pellet Plant In Hoyt Lakes, Minnesota (Permit No. 48B-95-1/O-1)*, Interpoll Laboratories, Inc., Circle Pines, MN, August 28, 1995.